


Product Dimensions, Standards and Weights

Metric DIN 921 Slotted Pan Head Screws with Large Head

Visit our online store for product availability

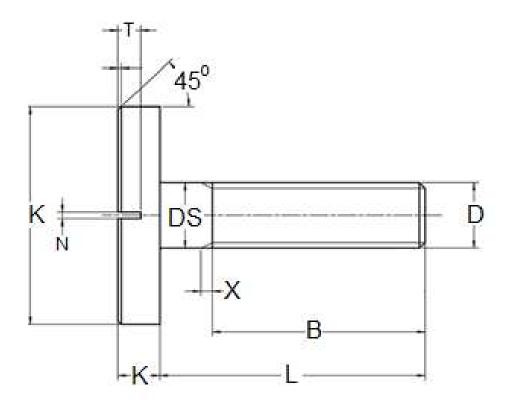

Dimensions of Metric DIN 921 slotted pan head screws with large head

Diameter (d)	M2	M3	M4	M5	M6	M8
Pitch	0.4	0.5	0.7	0.8	1	1.25
DK	6.00-5.64	8.00-7.64	12.00-11.57	16.00-15.57	20.00-19.48	25.00-24.48
K	1.32-1.08	1.92-1.68	2.52-2.28	2.82-2.58	3.25-2.95	3.95-3.65
N (nom)	0.5	0.8	1	1.2	1.6	2
T (min)	0.6	0.9	1.2	1.3	1.5	1.9

Aspen Fasteners 4807 Rockside Road, Suite 400, Independence, OH 44131 USA www.aspenfasteners.com | aspensales@aspenfasteners.com | 1-800-479-0056



Metric DIN 921 slotted pan head screws with large head have pan style head (cheese head) with a significantly larger diameter than a standard pan /cheese head. The large head screw would typically be used in applications where the extra weight bearing surface under the head is required to allow for more a even distribution of clamping forces. The wider diameter also eliminates the need for a washer and is very helpful when the size of the hole through which the screw is inserted is considerably larger than the diameter of the screw. Aspen Fasteners offers one of the most complete ranges of metric screws and other inch and metric industrial fasteners for immediate delivery from stock. The following sizes of DIN 921 slotted pan head screws with large head are available for immediate shipping from stock: Diameters ranging from M2 to M8 with lengths up to 25mm in stainless steel A2. View parts by clicking on the following link: DIN 921 slotted pan head screws with large head

DIN (**D**eutsches **I**nstitut für **N**ormung - German Institute for Standardization) standards are issued for a variety of components including industrial fasteners as Metric DIN 921 slotted pan head screws with large head. The DIN standards remain common in Germany, Europe and globally even though the transition to ISO standards is taking place. DIN standards continue to be used for parts which do not have ISO equivalents or for which there is no need for standardization.

Mechanical properties of stainless steel for metric DIN 921 slotted pan head screws with large head

Stainless steels can be divided into three groups of steel - austenitic, ferritic and martensitic. Austenitic steel is by

far the most common type (>90% of commercial fasteners). The steel groups and strength classes are designated by a four-digit sequence of letters and numbers (eg A2-70) as shown in the following table. DIN EN ISO 3506 governs screws and nuts made from stainless steel.

			Screws, Nuts and Bolts						
Steel group	Steel grade	Strength class	Tensile strength N/mm ²	Tensile strength PSI	Dia range	Nut Load N/mm ²			
		50	500	70,000	<=M39	500			
Austenitic	A2 and A4	70	700	100,000	<=M20	700			
		80	800	118,000	<=M20	800			

The tensile stress is calculated with reference to the tensile stress area (see DIN EN ISO 3506-1979). Nuts to be paired with same grade of stainless steel screws

Steel group	Property Strength class	Made From	Characteristics
	50	A1, A2	Soft; cold worked, turned and soft pressed fasteners
Austenitic	70	A2, A4	Cold worked, normal strength formed fasteners
	80	A2, A4	Extreme cold worked, high strength, special applications

Aspen Fasteners 4807 Rockside Road, Suite 400, Independence, OH 44131 USA www.aspenfasteners.com | aspensales@aspenfasteners.com | 1-800-479-0056



1) Chemical composition of stainless steel metric DIN 921 slotted pan head screws with large head

Grade	USA Grade	Material designation	Material no.	C %	Si ≤ %	Mn ≤ %	Cr %	Mo %	Ni %
A 2 304	X 5Cr Ni 1810	1.4301	≤ 0.07	1.0	2.0	17.5 to 19.5	ı	8.0 to 10.5	
	304	X 2 Cr Ni 1811	1.4306	≤ 0.03	1.0	2.0	18.0 to 20.0	-	10 to 12.0
		X 8 Cr Ni 19/10	1.4303	≤ 0.07	1.0	2.0	17.0 to 19.0	1	11.0 to 13.0
A 4	316	X 5 Cr Ni Mo 1712	1.4401	≤ 0.07	1.0	2.0	16.5 to 18.5	2.0 to 2.5	10.0 to 13.0
		X 2 Cr Ni Mo 1712	1.4404	≤ 0.03	1.0	2.0	16.5 to 18.5	2.0 to 2.5	10 to 13

2) Chemical composition of steel metric DIN 921 slotted pan head screws with large head

PROPERTY CLASS		CHEM	ICAL COMP	TEMPERING		
	MATERIAL AND TREATMENT	С		Р	S	TEMPERING TEMP °C MIN.
		min.	max.	max.	max.	
4.6, 4.8, 5.8, 6.8	Low or medium carbon steel	-	0.55	0.05	0.06	-
8.8	Medium carbon steel quenched, tempered	0.25	0.55	0.04	0.05	425
9.8	Medium carbon steel quenched, tempered	0.25	0.55	0.04	0.05	425
10.9	Medium carbon steel additives e.g. boron, Mn, Cr or Alloy steel - quenched, tempered	0.20	0.55	0.04	0.05	425
12.9	Alloy steel - quenched, tempered	0.20	0.50	0.035	0.035	380



3) Mechanical properties of steel for metric DIN 921 slotted pan head screws with large head

MECHANICAL PROPERTY			PROPERTY CLASS								
							8.8				
			4.8	5.6	5.8	6.8	Up to M 16	Over M 16	9.8	10.9	12.9
Tensile Strength	nom.		400	5	500	600	8	800		1000	1200
(Rm, N/mm²)	m	in.	420	500	520	600	800	830	900	1040	1220
Vickers Hardness	min.		130	155	160	190	250	255	290	320	385
Vickers naruness	max		250			320	336	360	380	435	
Brinell Hardness	min.		124	147	152	181	319	242	266	295	353
Brineii Hardness	max.		238			385	319	342	363	412	
	min.	HR	71	79	82	89			-		
RockwellHardness		HRC	-	-	-	-	20	23	28	32	39
RockwellHalulless	HR		95 99		-						
	max.	HRC	-	-	-	-	32	34	37	39	44
Yield Stress ReL.	nom.		320	300	400	480	-				
N/mm²	min.		340	300	420	480	-				
Stress at permanent	nom.				-		6	40	720	900	1080
set limit N/mm²	min.				-		640	660	720	940	1100

Disclaimer

Dimensional data and technical information for Metric DIN 921 slotted pan head screws with large head was obtained from publicly available sources and not acquired through standards agencies. It has been completed and compiled for reference purposes only; where discrepancies are found they are subject to change without notice. Aspen Fasteners makes no warranties or representations regarding the accuracy and validity of the compiled information and data. Contact the relevant standards authorities for accurate and detailed information.