


Metric ISO 15983 Open End Blind Rivets with Dome Head

Visit our [online store](#) for product availability

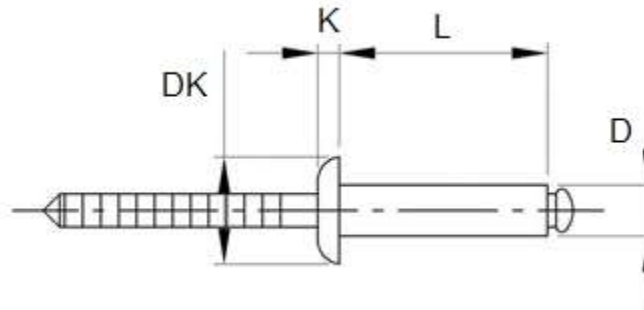

Dimensions of Metric ISO 15983 Open End Blind Rivets with Break Pull Mandrel and Dome Head

D	DK	K	grip length	L
2.4	5.0	.55	1 - 3	4
2.4	5.0	.55	3 - 5	6
2.4	5.0	.55	5 - 6.5	8
3	6.3	1.3	1 - 3	6
3	6.3	1.3	3 - 5	8
3	6.3	1.3	5 - 7	10
3	6.3	1.3	7 - 9	12
3	6.3	1.3	8 - 12	16
3.2	6.7	1.3	1 - 3	6
3.2	6.7	1.3	3 - 5	8
3.2	6.7	1.3	5 - 7	10
3.2	6.7	1.3	7 - 9	12
3.2	6.7	1.3	9 - 12	16

All measurements are in mm

D	DK	K	grip length	L
4	8.4	1.7	1 - 2.5	6

Aspen Fasteners 4807 Rockside Road, Suite 400, Independence, OH 44131 USA
www.aspenfasteners.com | aspensales@aspenfasteners.com | 1-800-479-0056



4	8.4	1.7	2.5 - 4.5	8
4	8.4	1.7	4.5 - 6.5	10
4	8.4	1.7	6.5 - 8.5	12
4	8.4	1.7	8.5 - 12	16
4	8.4	1.7	11.5 - 14	18
4	8.4	1.7	12 - 16	20
4.8	9.5	2	2 - 4	8
4.8	9.5	2	4 - 6	10
4.8	9.5	2	6 - 8	12
4.8	9.5	2	8 - 11	16
4.8	9.5	2	10 - 13	18
4.8	9.5	2	11 - 15	20
5	10.5	2.1	2 - 4	8
5	10.5	2.1	4 - 6	10
5	10.5	2.1	6 - 8	12
5	10.5	2.1	8 - 11	16
5	10.5	2.1	10 - 13	18
5	10.5	2.1	11 - 15	20
5	10.5	2.1	15 - 20	25
6.0	12	2.5	3 - 6	10
6.0	12	2.5	6 - 8	12
6.0	12	2.5	8 - 10	14
6.0	12	2.5	10 - 12	16
6.0	12	2.5	12 - 14	18
6.0	12	2.5	14 - 16	20
6.0	12	2.5	16 - 20	25
6.0	12	2.5	20 - 25	30
6.0	12	2.5	25 - 30	35
6.0	12	2.5	30 - 35	40
6.4	13	2.6	2 - 6	12
6.4	13	2.6	6 - 9	14
6.4	13	2.6	9 - 12	18
6.4	13	2.6	12 - 15	20
6.4	13	2.6	15 - 20	25

All measurements are in mm

Aspen Fasteners 4807 Rockside Road, Suite 400, Independence, OH 44131 USA
www.aspenfasteners.com | aspensales@aspenfasteners.com | 1-800-479-0056

Headquarters: Independence OH USA; Montreal QC Canada;
 Distribution Centers: Boston MA; Chicago IL; Cincinnati KY; Dallas TX; Denver CO; Houston TX; Jersey City NJ; Los Angeles CA; Miami FL;
 San Francisco CA; Seattle WA; Washington VA; Toronto ON; Calgary AB; Vancouver BC; Jiutepec (Temixco); Mexico City; Monterrey

Metric ISO 15983 Open End Blind Rivets with Break Pull Mandrel and Dome Head (also known as dome head break stem rivets) are tubular rivets with an integrated mandrel through the center. The rivet is inserted through a drilled hole in the parts to be fastened until the bearing surface of the dome head lies flush with the surface. A specialized tool is used to pull the mandrel back through the body of the rivet while holding the rivet in place. As the mandrel is pulled through the body it caused the blind end to deform outward until the mandrel snaps leaving a tightly riveted joint. Aspen Fasteners offers an extensive range of metric ISO 15983 Open End Blind Rivets with Dome Head as well other inch and metric industrial fasteners for immediate delivery from stock. The following sizes of metric ISO 15983 Open End Blind Rivets with Break Pull Mandrel and Dome Head are available for immediate shipping from stock: Diameters ranging from M2.4 to M6.4 in lengths up to 40mm, in stainless steel A2 and marine grade A4. View parts by clicking on the following link: [ISO 15983 Open End Blind Rivets with Break Pull Mandrel and Dome Head](#).

1) Mechanical properties of stainless steel for metric ISO 15983 Open End Blind Rivets with Break Pull Mandrel and Dome Head

Stainless steels can be divided into three groups of steel - austenitic, ferritic and martensitic. Austenitic steel is by far the most common type (>90% of commercial fasteners). The steel groups and strength classes are designated by a four-digit sequence of letters and numbers (eg A2-70) as shown in the following table. DIN EN ISO 3506 governs screws and nuts made from stainless steel.

Steel group	Steel grade	Strength class	Screws, Nuts and Bolts			
			Tensile strength N/mm ²	Tensile strength PSI	Dia range	Nut Load N/mm ²
Austenitic	A2 and A4	50	500	70.000	<=M39	500
		70	700	100.000	<=M20	700
		80	800	118.000	<=M20	800

The tensile stress is calculated with reference to the tensile stress area (see DIN EN ISO 3506-1979). Nuts to be paired with same grade of stainless steel screws

Steel group	Property Strength class	Made From	Characteristics
Austenitic	50	A1, A2	Soft; cold worked, turned and soft pressed fasteners
	70	A2, A4	Cold worked, normal strength formed fasteners

Aspen Fasteners 4807 Rockside Road, Suite 400, Independence, OH 44131 USA
www.aspenfasteners.com | aspensales@aspenfasteners.com | 1-800-479-0056

	80	A2, A4	Extreme cold worked. high strength. special applications
--	----	--------	--

2) Chemical composition of stainless steel metric ISO 15983 Open End Blind Rivets with Break Pull Mandrel and Dome Head

Grade	USA Grade	Material designation	Material no.	C %	Si ≤ %	Mn ≤ %	Cr %	Mo %	Ni %
A 2	304	X 5Cr Ni 1810	1.4301	≤ 0.07	1.0	2.0	17.5 to 19.5	-	8.0 to 10.5
		X 2 Cr Ni 1811	1.4306	≤ 0.03	1.0	2.0	18.0 to 20.0	-	10 to 12.0
		X 8 Cr Ni 19/10	1.4303	≤ 0.07	1.0	2.0	17.0 to 19.0	-	11.0 to 13.0
A 4	316	X 5 Cr Ni Mo 1712	1.4401	≤ 0.07	1.0	2.0	16.5 to 18.5	2.0 to 2.5	10.0 to 13.0
		X 2 Cr Ni Mo 1712	1.4404	≤ 0.03	1.0	2.0	16.5 to 18.5	2.0 to	10 to 13

3) Chemical composition of steel metric ISO 15983 Open End Blind Rivets with Break Pull Mandrel and Dome Head

PROPERTY CLASS	MATERIAL AND TREATMENT	CHEMICAL COMPOSITION LIMITS %				TEMPERING TEMP °C MIN.
		C		P	S	
		min.	max.	max.	max.	
4.6. 4.8. 5.8. 6.8	Low or medium carbon steel	-	0.55	0.05	0.06	-
8.8	Medium carbon steel quenched. tempered	0.25	0.55	0.04	0.05	425
9.8	Medium carbon steel quenched. tempered	0.25	0.55	0.04	0.05	425
10.9	Medium carbon steel additives e.g. boron. Mn. Cr or Alloy steel - quenched. tempered	0.20	0.55	0.04	0.05	425
12.9	Alloy steel - quenched. tempered	0.20	0.50	0.035	0.035	380

Aspen Fasteners 4807 Rockside Road, Suite 400, Independence, OH 44131 USA
www.aspenfasteners.com | aspensales@aspenfasteners.com | 1-800-479-0056

4) Mechanical properties of steel for metric ISO 15983 Open End Blind Rivets with Break Pull Mandrel and Dome Head

MECHANICAL PROPERTY		PROPERTY CLASS									
		4.8	5.6	5.8	6.8	8.8		9.8	10.9	12.9	
						Up to M 16	Over M 16				
Tensile Strength (Rm. N/mm ²)	nom.	400	500		600	800		900	1000	1200	
	min.	420	500	520	600	800	830	900	1040	1220	
Vickers Hardness	min.	130	155	160	190	250	255	290	320	385	
	max.	250				320	336	360	380	435	
Brinell Hardness	min.	124	147	152	181	319	242	266	295	353	
	max.	238				385	319	342	363	412	
Rockwell Hardness	min. HR	71	79	82	89	-					
	HRC	-	-	-	-	20	23	28	32	39	
	HR	95				99	-				
	max. HRC	-	-	-	-	32	34	37	39	44	
Yield Stress ReL. N/mm ²	nom.	320	300	400	480	-					
	min.	340	300	420	480	-					
Stress at permanent set limit N/mm ²	nom.	-				640		720	900	1080	
	min.	-				640	660	720	940	1100	

Disclaimer

Dimensional data and technical information for metric ISO 15983 Open End Blind Rivets with Break Pull Mandrel and Dome Head was obtained from publicly available sources and not acquired through standards agencies. It has been completed and compiled for reference purposes only; where discrepancies are found they are subject to change without notice. Aspen Fasteners makes no warranties or representations regarding the accuracy and validity of the compiled information and data. Contact the relevant standards authorities for accurate and detailed information.