


Metric DIN 963 Slotted Flat Countersunk Head Machine Screws

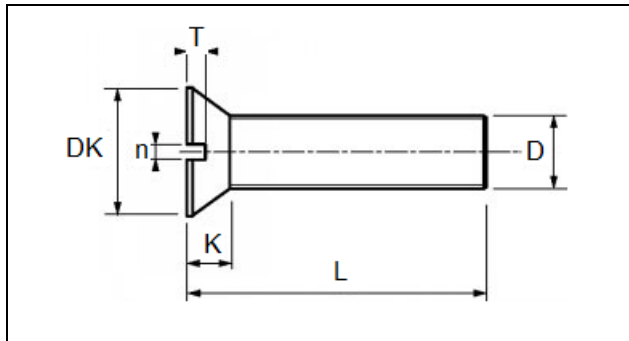

Thread D		M1	M1.2	M1.4	M1.6	M2	M2.5	M3	M4	M5	M6	M8	M10	M12	M16	M20
P		0.25	0.25	0.3	0.35	0.4	0.45	0.5	0.7	0.8	1	1.25	1.5	1.75	2	2.5
A	max.	0.5	0.5	0.6	0.7	0.8	0.9	1	1.4	1.6	2	2.5	3	3.5	4	5
B	min.	full thread			15	16	18	19	22	25	28	34	40	46	58	70
DK	nominal															
	max.	1.9	2.3	2.6	3	3.8	4.7	5.6	7.5	9.2	11	14.5	18	22	29	36
DK	min.	1.76	2.06	2.46	2.86	3.5	4.4	5.3	7.14	8.9	10.6	14.1	17.6	21.5	28.5	35.4
K	max.	0.6	0.72	0.86	0.96	1.2	1.5	1.65	2.2	2.5	3	4	5	6	8	10
n	nominal	0.25	0.3	0.3	0.4	0.5	0.6	0.8	1	1.2	1.6	2	2.5	3	4	5
	max.	0.31	0.36	0.36	0.46	0.56	0.66	0.86	1.06	1.26	1.66	2.06	2.56	3.06	4.07	5.07
	min.	0.45	0.5	0.5	0.6	0.7	0.8	1	1.2	1.51	1.91	2.31	2.81	3.31	4.37	5.37
r	max.	0.1	0.12	0.14	0.16	0.2	0.25	0.3	0.4	0.5	0.6	0.8	1	1.2	1.6	2
T	min.	0.2	0.25	0.28	0.32	0.4	0.5	0.6	0.8	1	1.2	1.6	2	2.4	3.2	4
	max.	0.3	0.35	0.4	0.45	0.6	0.7	0.85	1.1	1.3	1.6	2.1	2.6	3	4	5
X	max.	-	-	-	0.9	1	1.1	1.25	1.75	2	2.5	3.2	3.8	4.4	5	6.3

All measurements are in mm

Metric DIN 963 are slotted drive flat countersunk head machine screws. Metric machine screws are designed for metal to metal applications requiring a pre-drilled hole and a mating metric nut for the screw to thread into. These screws are usually fully threaded with machine threads and blunt point. The recommended pre-drilled hole sizes vary depending on the diameter of the screw to be used but should be slightly larger in diameter than the major (maximum) thread diameter. These screws are available in zinc plated steel as well as stainless steel A2 and A4. Metric flat countersunk heads have a flat top surface and a cone-shaped bearing surface with a head angle of approximately 90°. They are used for applications where the head must be flush with the mating surface of the substrate. Aspen Fasteners offers over 500.000 unique fastener products from stock in inch and metric standard in a variety of materials and finishes. The following sizes of metric DIN 963 slotted drive flat countersunk head machine screws are available for immediate shipping from stock: Diameters ranging from M1 to M20 up to 100mm long in zinc plated steel and stainless steel A2 and A4. View parts by clicking on the following link: [DIN 963 slotted drive flat countersunk head machine screws](#)

Thread D			M1	M1.2	M1.4	M1.6	M2	M2.5	M3	M4	M5	M6	M8	M10	M12	M16	M20	
L			weight kg/1000pcs															
nominal	min.	max.																
2	1.8	2.2	0.01	0.02	0.03	0.05												
3	2.8	3.2	0.02	0.03	0.04	0.06	0.1	0.18										
4	3.75	4.25	0.02	0.04	0.05	0.07	0.12	0.21	0.29									
5	4.75	5.25	0.03	0.04	0.06	0.08	0.14	0.24	0.34	0.68								
6	5.75	6.25		0.05	0.07	0.09	0.15	0.27	0.38	0.75	1.21							
8	7.7	8.3			0.09	0.12	0.19	0.33	0.47	0.9	1.45	2.19						
10	9.7	10.3			0.11	0.14	0.23	0.39	0.56	1.06	1.7	2.54	5.03					
12	11.7	12.4					0.27	0.45	0.64	1.22	1.95	2.89	5.67	9.59				
14	13.7	14.4					0.31	0.51	0.73	1.37	2.19	3.25	6.3	10.6				
16	15.7	16.4					0.34	0.57	0.82	1.53	2.44	3.61	6.94	11.6				
18	17.7	18.4					0.38	0.63	0.91	1.68	2.69	3.95	7.57	12.6				
20	19.6	20.4						0.69	1	1.84	2.94	4.31	8.21	13.6	20.8			
22	21.6	22.4						0.75	1.08	1.99	3.18	4.66	8.84	14.6	22.2			
25	24.6	25.4						0.84	1.22	2.22	3.55	5.19	9.79	16.1	24.4	47.7		
28	27.6	28.4							1.35	2.46	3.93	5.72	10.7	17.6	26.6	51.7		
30	29.6	30.4							1.44	2.61	4.16	6.08	11.4	18.6	28.1	54.4	90.5	
35	34.5	35.5								2.99	4.76	6.96	13	21.1	31.7	61.1	101	
40	39.5	40.5								3.36	5.39	7.84	14.6	23.6	35.3	67.6	111	
45	44.5	45.5									6.02	8.73	16.2	26.1	39	74.5	122	
50	49.5	50.5									6.65	9.61	17.8	28.6	42.6	81.1	132	
55	54	56											19.4	31.1	46.2	87.8	143	
60	59	61												33.7	49.8	94.4	153	
70	69	71													51.7	108	174	
80	79	81													64.4	121	195	
90	89	91														134	216	
100	99	101														148	237	

DIN (Deutsches Institut für Normung - German Institute for Standardization) standards are issued for a variety of components including industrial fasteners as metric DIN 963 slotted drive flat countersunk head machine screws. The DIN standards remain common in Germany, Europe and globally even though the transition to ISO standards is taking place. DIN standards continue to be used for parts which do not have ISO equivalents or for which there is no need for standardization. The ISO equivalent of a metric DIN 963 slotted drive flat countersunk head machine screws is ISO 2009.

1) Mechanical properties of stainless steel for metric DIN 963 slotted drive flat countersunk head machine screws

Stainless steels can be divided into three groups of steel - austenitic, ferritic and martensitic. Austenitic steel is by far the most common type (>90% of commercial fasteners). The steel groups and strength classes are designated by a four-digit sequence of letters and numbers (eg A2-70) as shown in the following table. DIN EN ISO 3506 governs screws and nuts made from stainless steel.

Steel group	Steel grade	Strength class	Screws, Nuts and Bolts			
			Tensile strength N/mm ²	Tensile strength PSI	Dia range	Nut Load N/mm ²
Austenitic	A2 and A4	50	500	70.000	<=M39	500
		70	700	100.000	<=M20	700
		80	800	118.000	<=M20	800

The tensile stress is calculated with reference to the tensile stress area (see DIN EN ISO 3506-1979). Nuts to be paired with same grade of stainless steel screws

Steel group	Property Strength class	Made From	Characteristics
Austenitic	50	A1, A2	Soft; cold worked, turned and soft pressed fasteners
	70	A2, A4	Cold worked, normal strength formed fasteners
	80	A2, A4	Extreme cold worked, high strength, special applications

2) Chemical composition of stainless steel metric DIN 963 slotted drive flat countersunk head machine screws

Grade	USA Grade	Material designation	Material no.	C %	Si ≤ %	Mn ≤ %	Cr %	Mo %	Ni %
A 2	304	X 5Cr Ni 1810	1.4301	≤ 0.07	1.0	2.0	17.5 to 19.5	-	8.0 to 10.5
		X 2 Cr Ni 1811	1.4306	≤ 0.03	1.0	2.0	18.0 to 20.0	-	10 to 12.0
		X 8 Cr Ni 19/10	1.4303	≤ 0.07	1.0	2.0	17.0 to 19.0	-	11.0 to 13.0
A 4	316	X 5 Cr Ni Mo 1712	1.4401	≤ 0.07	1.0	2.0	16.5 to 18.5	2.0 to 2.5	10.0 to 13.0
		X 2 Cr Ni Mo 1712	1.4404	≤ 0.03	1.0	2.0	16.5 to 18.5	2.0 to 2.5	10 to 13

3) Chemical composition of steel metric DIN 963 slotted drive flat countersunk head machine screws

PROPERTY CLASS	MATERIAL AND TREATMENT	CHEMICAL COMPOSITION LIMITS %				TEMPERING TEMP °C MIN.
		C		P	S	
		min.	max.	max.	max.	
4.6. 4.8. 5.8. 6.8	Low or medium carbon steel	-	0.55	0.05	0.06	-
8.8	Medium carbon steel quenched. tempered	0.25	0.55	0.04	0.05	425
9.8	Medium carbon steel quenched. tempered	0.25	0.55	0.04	0.05	425
10.9	Medium carbon steel additives e.g. boron. Mn. Cr or Alloy steel - quenched. tempered	0.20	0.55	0.04	0.05	425
12.9	Alloy steel - quenched. tempered	0.20	0.50	0.035	0.035	380

Aspen Fasteners 4807 Rockside Road, Suite 400, Independence, OH 44131 USA
www.aspenfasteners.com | aspensales@aspenfasteners.com | 1-800-479-0056

4) Mechanical properties of steel for metric DIN 963 slotted drive flat countersunk head machine screws

MECHANICAL PROPERTY		PROPERTY CLASS								
		4.8	5.6	5.8	6.8	8.8		9.8	10.9	12.9
						Up to M 16	Over M 16			
Tensile Strength (Rm. N/mm ²)	nom.	400	500		600	800		900	1000	1200
	min.	420	500	520	600	800	830	900	1040	1220
Vickers Hardness	min.	130	155	160	190	250	255	290	320	385
	max.	250				320	336	360	380	435
Brinell Hardness	min.	124	147	152	181	319	242	266	295	353
	max.	238				385	319	342	363	412
Rockwell Hardness	min. HR	71	79	82	89	-				
	HRC	-	-	-	-	20	23	28	32	39
	HR	95			99	-				
	max. HRC	-	-	-	-	32	34	37	39	44
Yield Stress ReL. N/mm ²	nom.	320	300	400	480	-				
	min.	340	300	420	480	-				
Stress at permanent set limit N/mm ²	nom.	-				640		720	900	1080
	min.	-				640	660	720	940	1100

Disclaimer

Dimensional data and technical information for metric DIN 963 slotted drive flat countersunk head machine screws was obtained from publicly available sources and not acquired through standards agencies. It has been completed and compiled for reference purposes only; where discrepancies are found they are subject to change without notice. Aspen Fasteners makes no warranties or representations regarding the accuracy and validity of the compiled information and data. Contact the relevant standards authorities for accurate and detailed information.